

Mechanical characterization of AISI 316 tubes filled with Al alloy foams

G. Costanza, A. Sili, M.E.Tata

In tubular elements filled with metal foams the structural collapse is delayed in comparison with the empty tubes, consequently compression strength and absorbed energy increase. Production methods of foams are crucial, as they determine cellular morphology and bonds formation with tube wall. In this work AISI 316 steel tubes filled with foam of commercially pure Al and Al-Si alloys with hypoeutectic compositions were produced. The process parameters were optimized to obtain closed cells foams with an acceptable morphology of porosity and good mechanical properties. Foams were characterized by optical and scanning electron microscopy and by computer tomography; mechanical properties were investigated by axial compression tests (performed on foam samples and on Cu tubes, empty or filled with foams) and radial compression "Brazilian test" (carried out on AISI 316 tubes, empty or filled with foams).

Keywords: Aluminum foams - Metallography - Mechanical Testing - Non-destructive testing - Processes

INTRODUCTION

In the automotive industry particular attention has been oriented to the utilization of structural elements as energy absorbers, in order to guarantee good passenger protection by transforming, in the event of collision, kinetic energy in deformation energy [1]. Cellular materials, as metal foams, light and high energy absorber, are very attractive in automotive applications where crashworthiness, fuel saving and CO₂ emission restraint are critical parameters [2].

In recent years, aluminum foams have been widely used thanks to their low density and melting point which facilitate production process [3]. Their porous structure allows to absorb significant amounts of energy at constant and relatively low stress; in particular compression behavior is affected by cells morphology, as quoted in literature through experimental surveys [4,5] and numerical simulation [6]. Strain rate is critical for compression behavior of foams [7]: in quasi-static conditions, the compression diagram of a closed-cell Al foam is characterized by a short initial elastic phase, a broad plateau of plastic deformation (up to strain around 50-60%), with the gradual disappea-

rance of cells of greater diameter, and a final stage with a sudden load increase due to cells collapse in the whole sample [8]. Compression properties, such as elastic modulus, plastic plateau wideness and related absorbed energy depends on the collapse mode of cells [9, 10], which are affected by production process parameters [11]. In this field computer tomography has been experimented as a useful tool for observing, step by step, compression of a single sample [8].

Metallic tubes filled with Al foam cores are attractive because of the interaction between tube wall and foam which delays the structural collapse and increases energy absorption during compression or bending [12]. The efforts of many researchers have been directed towards the optimization of foaming conditions inside tubes [13], testing the effects of such filling on impact energy absorption in structural components [14], developing numerical simulation in order to study the buckling patterns [15] and carrying out size optimization of a hollow tube acting as energy absorber, evaluating also the effects of filling [16]. During deformation of a tube filled with metal foam, the collapse mode of cells and their interaction with the container inner surface play an important role. As regards the production process, it is necessary to avoid the formation of an insulating oxide film between foam and tube internal surface: the possibility of obtaining the formation of metallurgical bonds through foaming in situ with appropriate precautions was experimented in [17]. A careful investigation of metal foams and filled tubular elements requires the preparation of numerous specimens at different compression levels, in order to perform a 3D reconstruction

G. Costanza, M.E.Tata

Dipartimento di Ingegneria Industriale, Università di Roma - Tor Vergata

A. Sili

Dipartimento di Ingegneria Elettronica, Chimica e Ingegneria Industriale, Università di Messina

during deformation of both cells structure [18] and the whole foam/tube system [19].

In a previous work [19], copper tubes filled with aluminum foam were produced through a foaming compacted powders inside them: the axial compression behavior of these elements was studied by means of tomographic observations carried out at various levels of compression.

In this work AISI 316 steel tubes filled with foam of commercially pure Al and Al-Si hypoeutectic alloy are produced too. The first goal has been the process parameters optimization to obtain closed cells foams with an acceptable morphology of porosity and good mechanical properties, successively manufacturing filled tubes to be utilized as energy absorber. Foams were metallographically characterized by optical and scanning electron microscopy (SEM) and by computer tomography (CT); mechanical properties were investigated by axial compression test on foams samples and copper tubes (empty or filled) and radial compression "Brazilian test" on AISI 316 tubes (empty or filled).

MATERIALS AND METHODS

Foams production

Foams production was performed by compacted powders method [20]. On the basis of the process parameters developed in previous work [21 - 24], foams with closed cells of AlSi hypoeutectic alloys were produced. Silicon lowers the melting point of aluminum making it closer to that of the foaming agent decomposition (465°C). Such alloying gives a remarkable increase of hardness than pure aluminum, improving wear resistance and mechanical properties in general; however, an excess of Si gives excessive fluidity making difficult to control bubbles growth; moreover Si can significantly embrittle the cells walls carrying to collapse during deformation.

Commercially pure Al powder (96.6%), alone or with Al-Si12 alloy powder to obtain hypoeutectic compositions (both 44 µm average diameter), was suitable mixed with TiH₂ powder as foaming agent (5 µm average diameter) and SiC powder (37 µm average diameter) to increase viscosity and stabilize porosity by acting on the interface metal - bubble.

The following compositions were considered: TiH₂ (0.4 - 0.6 weight %), SiC (3 - 9 weight %) and metals powder (commercially pure Al, alone or together with AlSi12) to balance. These powders were carefully mixed to have a homogeneous precursor, because, especially for TiH₂ particles, it is a fundamental requirement for producing foams of good quality [25].

In order to obtain precursors with diameter of 15 mm and height of 10 mm, powder mixtures were compacted in a mold, by means of hydraulic press, choosing the optimum load for crushing any oxide inside powders (120 kN for commercially pure Al and 150 kN for Al-Si alloys, as a consequence of their greater mechanical strength). The oxide layer was removed from the precursor surface by mechanical abrasion, to avoid any obstacle to bubble growth du-

ring foaming. Precursors were placed inside Cu tubes or AISI 316 steel tubes: both tubes were 16 mm diameter and 1 mm thickness and were utilized as crucibles inside a furnace at 700°C (optimal temperature for a continuous H₂ release) for 5 min (in the case of Cu tubes) or 8 min (AISI 316 tubes). Then samples were extracted from the furnace and water cooled. These combinations of process temperature and time were experimented as suitable for a good compromise between melt viscosity and foam growth.

Metallographic and tomographic investigations

Samples of foams and tube sections, after appropriate metallographic preparation and etching with HF (0.5%), were observed by optical microscopy and SEM. Moreover, CT investigations were performed by a variable focus apparatus (Cu filament and X-ray accelerating voltage of 225 kV), operating in the field of micro-macro focus with spatial resolution up to 30 microns. The 2D images of tube sections were elaborated to increase contrast and brightness in order to highlight cells structure and foam - wall interfaces.

Compression tests

Compression tests were performed on cylindrical specimens of foams and tubes (empty or filled) at crosshead constant speed (2 mm/min), with a data acquisition frequency of 5 Hz. For safety reasons, the maximum load did not exceed 45 kN, being the load cell capacity equal to 50 kN.

Axial compression test

Axial compression tests were carried out to compare commercially pure Al and Al-Si alloys behaviors, excluding tube stiffening effects. Results of axial compressions on Cu tubes filled with Al foam, performed step by step to take tomographic images, were also reported [19].

Compression stress is given by the following equation:

$$1) \quad \sigma = 4 P / (\pi D^2)$$

being P the applied load and D the specimen diameter, assumed equal to the initial value.

The deformation ϵ was referred to the crosshead advancement (δ):

$$2) \quad \epsilon = (L - L_o) / L_o = \delta / L_o$$

where L is the length of the deformed specimen and L_o its initial length.

Radial compression test

On steel tubes, because of their higher stiffness compared to copper tubes, were carried out radial compression tests, named "Brazilian test". This test is used in the field of rocks, powder metallurgy [26] and in any case tensile test cannot be performed [27]. As shown in figure 1, it gives rise to compression stresses along the direction of compression (y) and tensile stresses along the perpendicular direction (x).

The compression (σ_y) and tensile (σ_x) stresses along the y axis achieve their maximum values at the origin and assume the following expressions [27]:

$$3) \quad \sigma_y = -6P / (\pi D l)$$

$$\sigma_x = 2P / (\pi D l)$$

where l is the axial length of the specimen and D is assumed equal to the initial diameter.

Deformation values were calculated on the basis of the diameter values along the direction of compression according to the following expression:

$$4) \quad \varepsilon = (D_o - D) / D_o$$

being D_o the initial diameter.

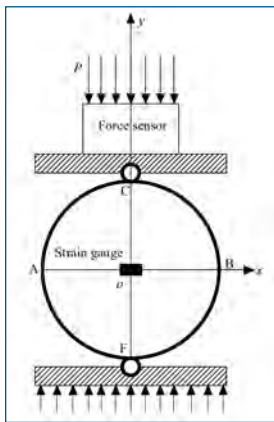


Fig. 1 - Sketch of the radial compression test "Brazilian test": y compression stress and x tensile stress directions.

Fig. 1 - Schema della prova di compressione radiale "Brazilian test": y direzione degli sforzi di compressione, x direzione degli sforzi di trazione.

RESULTS AND DISCUSSION

Process parameters optimization

The best quality of cells morphology was achieved with commercial pure Al: samples of AISI 316 tube and Cu tube filled with commercially pure Al are shown in fig. 2, where the CT image appears suitable to check the bonding conditions between foam and tube wall.

The AISi6 and AISi8 foams had good quality, even if some problems of cells coalescence were encountered. Figure 3 shows three samples of AISi6 alloy, with 0.4% of TiH₂ and different concentrations of SiC. The SiC particles have the dual effect of increasing liquid viscosity and stabilize porosity: Banhart's work shows how improvements can be achieved by stabilizing bubbles growth during foaming [29]. In our experiments the optimal content of the stabilizer agent SiC resulted equal to 9%, greater than the quantity of 3% utilized for pure Al foam, while the blowing agent content was the same (0.4% of TiH₂).

About the Si content in the matrix, the best result in terms of cell morphology (size, shape and regular distribution) was obtained with the AISi8 alloy, while other compositions had problems of cells coalescence. In any case these problems are common to all the AISi alloys, due to higher foaming time in the steel crucible.

In figure 4 two samples of AISi8 foams with two different content of the blowing agent TiH₂ are shown: titanium

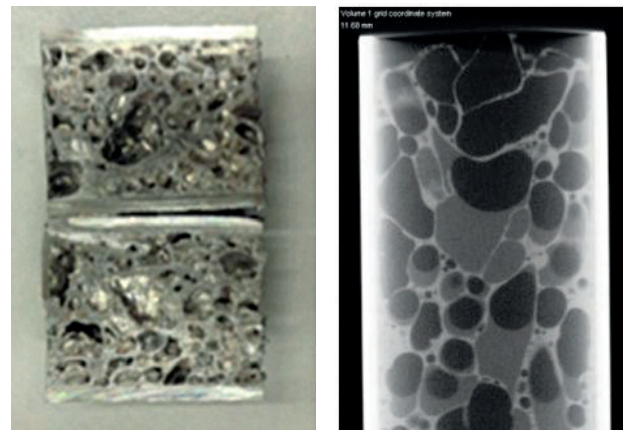


Fig. 2 - Samples of tubes filled with commercially pure Al foam: a) steel tube (photographic image of a section), b) Cu tube (CT image).

Fig. 2 - Campioni di tubi riempiti con schiuma in Al commercialmente puro: a) tubo di acciaio (immagine fotografica del tubo sezionato), b) tubo di rame (immagine tomografica).

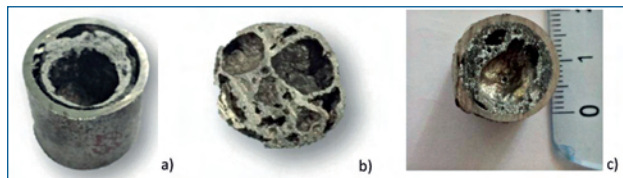


Fig. 3 - Effect of SiC content on foaming process (AISi6 alloy - TiH₂ 0.4%): a) 3%, b) 9%, c) 12%.

Fig. 3 - Effetto del tenore di SiC sul processo di schiumatura (lega AISi6 - TiH₂ 0.4%): a) 3%, b) 9%, c) 12%.

hydride begins to dissociate above 465°C, giving rise to bubbles of H₂ and causing the molten metal expansion and the consequent filling of the crucible.

The TiH₂ and SiC contents determine density and, according to the cooling conditions, cells size: the best cell morphology was obtained with a TiH₂ content equal to 0.4%.

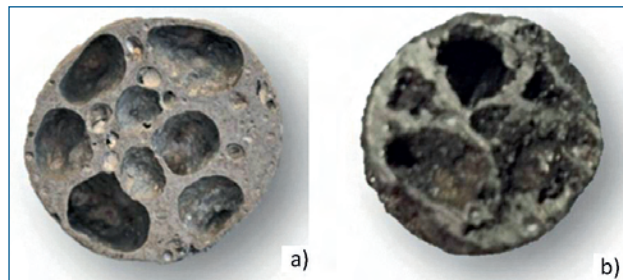


Fig. 4 - Effects of TiH₂ content on foaming process (AISi8 - SiC 9%): a) 0.4%, b) 0.6%.

Fig. 4 - Effetto del tenore di TiH₂ sul processo di schiumatura (lega AISi8 - SiC 9%): a) 0.4%, b) 0.6%.

Metallographic investigations

Metallographic investigations confirmed the hypoeutectic alloy formation. Due to the high melting point, the SiC particles are dispersed in the metal matrix and are perfectly visible at low magnification (fig. 5a). The metal matrix has a hypoeutectic morphology with primary Al grains and Si precipitates at their boundary, clearly recognizable at higher magnification (fig. 5b). The Si particles have average dimension of about 1 μm (fig. 6).

Compression test

The compression curves of three foam samples (commercially pure Al, AlSi6 and AlSi8), not contained in tubes, are compared in figure 7: both compression strength and absorbed energy increase with the Si content. The Al foam has a progressive strain hardening according to deformation. Instead the AlSi alloys curves are characterized by an initial peak, followed by stress reductions at deformations above 20%, ascribed to cells collapse due to the alloy brittleness, or other factors such as polyhedral shape cavities that give rise to a triaxial stress state. In all the examined cases, at deformations around 80%, stress increases sharply as a result of the generalized cells collapse.

At the end of compression test, the Al foam deformed into a thin homogeneous disk, while the AlSi ones show some fractures that can be ascribed to crack nucleation caused by the combined effects of SiC sharp edges and alloy brittleness.

Cu tubes filled with commercially pure Al foam have a stiffness significantly greater than those of empty tubes, as shown in figure 8 [19]. Their compression behavior is characterized by a sequence of peaks, each one corresponding to wall buckling.

Cu tube filled with Al foam started buckling with the first two folds located at the two ends of the sample, while the third fold grows at half height; instead the empty tube started to buckle at one of the two ends and continues sequentially. During the initial stage of deformation (fig. 9a), the cells remain intact and adherent to the tube wall, with localized detachments at the first fold or at the zones where folds are to be formed. At successive deformation step (fig. 9b) cells appear strongly damaged with evident detachment from tube walls.

Radial compression curves of the AISI 316 tubes, respectively empty and filled with commercially pure Al or AlSi8 alloy foams, are shown in figure 10. All the three diagrams show a wide plateau of plastic deformation. In general foam increases the tube stiffness, anyway the AlSi8 foam is more performing in terms of mechanical strength and absorbed energy, although Si entails a weight increase.

CONCLUSIONS

Conclusions are drawn with reference to the following topics: foaming parameter optimization, metallurgical and mechanical characterization of foams, mechanical behavior of tubes filled with foam. Regarding the first point,

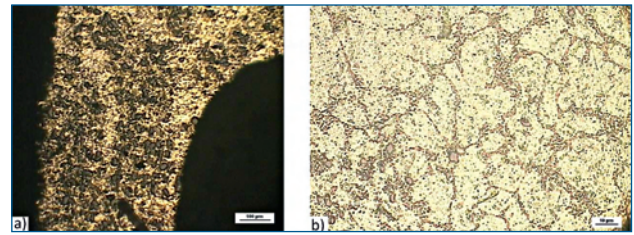


Fig. 5 – Optical micrographs of AlSi6 foam: a) cell wall with SiC particles, b) detail of metal matrix.

Fig. 5 – Micrografie ottiche di una schiuma in lega AlSi6: a) parete di una cellula con evidenza delle particelle di SiC, b) dettaglio della matrice metallica.

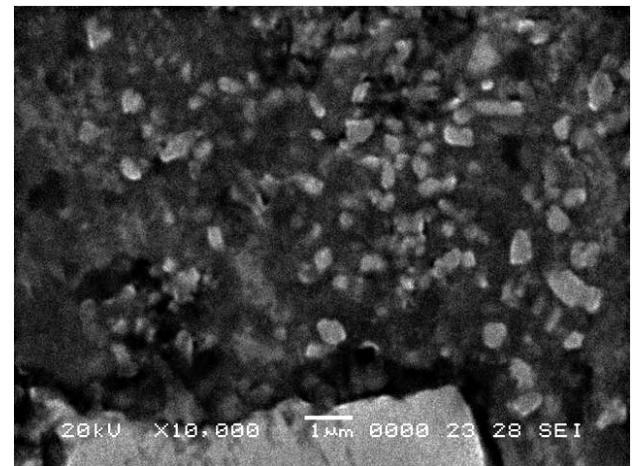


Fig. 6 – SEM micrograph of AlSi6 foam.

Fig. 6 – Micrografia SEM di una schiuma in lega AlSi6.

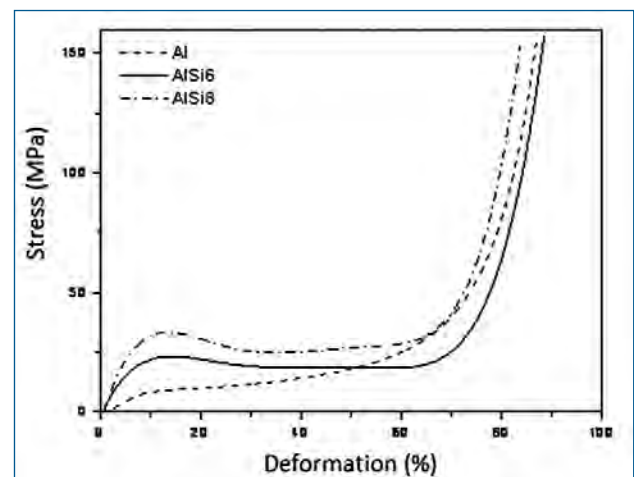


Fig. 7 – Compression diagrams: commercially pure Al and AlSi alloys foams.

Fig. 7 – Diagrammi di compressione: schiume in Al commercialmente puro e leghe AlSi.

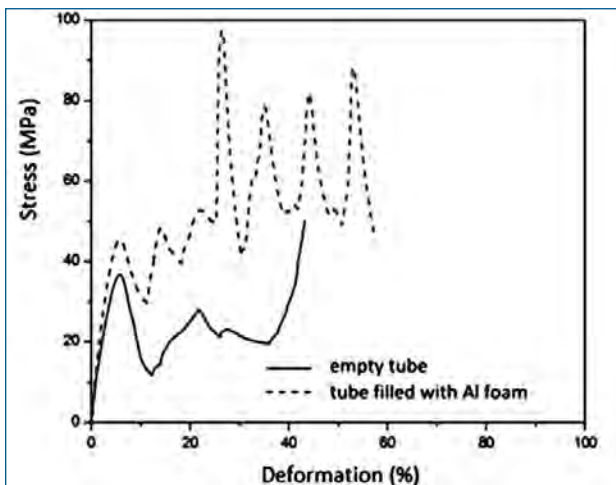


Fig. 8 – Compression diagrams: empty Cu tube, Cu tube filled with commercially pure Al.

Fig. 8 – Diagrammi di compressione: tubo di Cu vuoto, tubo di Cu riempito con schiuma in Al commercialmente puro.

commercially pure Al and AlSi alloy foams of good quality were obtained starting from compacted powders, thanks to the optimization of blowing and stabilizer agents contents according to process time and temperature.

Commercial pure Al foams showed the best morphology quality of cells; the AlSi6 and AlSi8 foams had a good quality too, even if some problems of cells coalescence were encountered. Greater compression strength and absorbed energy were achieved testing the AlSi hypoeutectic alloys, in particular both the two properties increased if the Si content changed from 6 to 8 %.

Finally it was experimented that compression strength and absorbed energy of Cu and AISI 316 tubes filled with foams are significantly greater than those of empty tubes. During axial compression, Cu tubes showed characteristic buckling folds and related peaks in the stress - strain curve; instead the AISI 316 tubes, tested by radial compression, gave continuous curves.

ACKNOWLEDGEMENTS

We would like to thank Mr. Piero Plini and Mr. Benedetto Iacovone for technical support during mechanical testing; Dr. Francesco Brugnolo and Dr. Livio Longobardi, who contributed actively to this research carrying out their thesis.

REFERENCES

- 1] G. Dong, D. Wang, J. Zhang, S. Huang, "Side Structure Sensitivity to Passenger Car Crashworthiness During Pole Side Impact", *Tsinghua Science and Technology*, 12(3) (2007). 290-295
- 2] G. Lu and T. Yu, "Energy absorption of structures and materials", Woodhead Publishing Limited, Cambridge, UK, (2003), 1-424

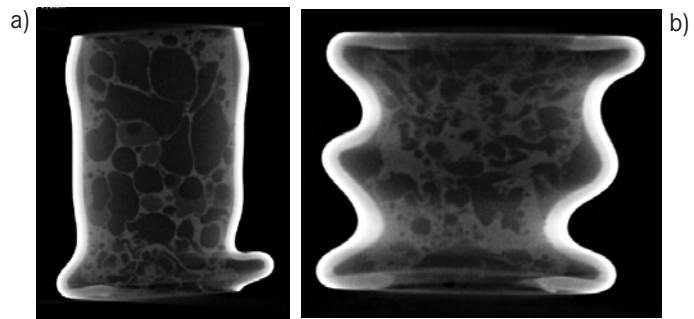


Fig. 9 – Tomographic sections at two deformation steps of a Cu samples filled with Al foam: a) initial deformation stage; b) after deformation (50%).

Fig. 9 – Sezioni tomografiche a due livelli di deformazione di un tubo di rame riempito con schiuma in alluminio: a) fase iniziale della deformazione; b) fase avanzata (50%).

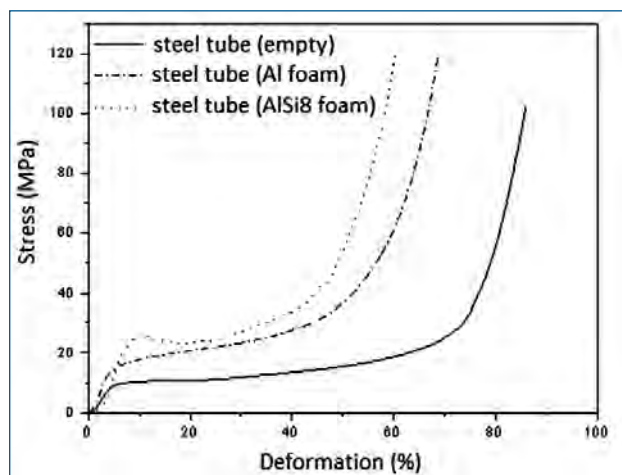


Fig. 10 – Radial compression "Brazilian test" results (compression stress according to diametral deformation)

Fig. 10 – Risultati della prova di compressione radiale "Brazilian test" (sforzi di compressione in funzione della deformazione diametrale).

- 3] M. Yu, J. Banhart, "Mechanical properties of metal foams", in *Metal Foams*, Ed. J. Banhart and H. Eifert, Verlag MIT, Bremen (1998), 37-48
- 4] H. Yu, Z. Guo, Bing Li, G. Yao, H. Luo, Y. Liu, "Research into the effect of cell diameter of aluminium foam on its compressive and energy absorption properties", *Material Science and Engineering A*, 454-455 (2007), 542-546
- 5] F. Campana, D. Pillone, "Effect of wall microstructure and morphometric parameters on the crush behaviour of Al alloy foams", *Materials Science and Engineering A*, 479 (2008), 58-64
- 6] Yang An, Cui'e Wen, Peter D. Hodgson, Chunhui Yang, "Investigation of cell shape effect on the mechanical behaviour of open-cell metal foams", *Computational*

- Science, 55 (2012), 1-9
- 7] G. Costanza, M.E. Tata, "Dynamic and static compressive behaviour of aluminium foam", Proceedings of the 4th International Structural Engineering and Construction Conference, ISEC-4 - Innovations in Structural Engineering and Construction, Vol. 2 (2008) 919-922
 - 8] G. Costanza, F. Mantineo, S. Missori, A. Sili, M.E. Tata, "Characterization of the compressive behaviour of an Al foam by X-ray computerized tomography", TMS 2012 - 141st Annual Meeting & Exhibition, March 11-15 2012, Orlando FL., Light Metals 2012, Edited by Carlos E. Suarez, John Wiley & Sons, pp. 533-536
 - 9] H.W. Song, Q.J. He, J.J. Xie, A. Tobota, "Fracture mechanisms and size effects of brittle metallic foams: in situ compression test inside SEM", Composites Science and Technology, 68 (2008), 2441-2450
 - 10] Y. Mu, G. Yao, L. Liang, H. Luo, G. Zu, "Deformation mechanisms of closed-cell aluminium foam in compression", Scripta Materialia, 63 (2010), 629-632
 - 11] G. Costanza, R. Montanari, M.E. Tata, "Optimisation of TiH₂, and SiC content in Al foams", La Metallurgia Italiana, Vol. 97 n. 6 (2005), 41-47.
 - 12] M. Seitzberger, F.G. Rammerstorf, H.P. Degischer, R. Gradinger, "Crushing of axially compressed steel tubes filled with aluminium foam", Acta Mechanica, 125 (1997), 93-105.
 - 13] Makoto Kobashi, Ryosuke Sato, Naoyuki Kanetake, "Foaming and filling-in behavior of porous aluminum in hollow components", Materials Transactions, V. 47, No 9 (2006), 2178-2182.
 - 14] Y. An, Cui'e G Wen, P. Hodgson, C. Yang "Impact response and energy absorption of aluminum foam-filled tubes"; Applied Mechanics and Materials, V. 152-154 (2012), 436-439
 - 15] Wenyi Yan, Emilien Durif, Yasuo Yamada, Cui'e Wen, "Crushing simulation of foam-filled aluminium tubes", Materials Transactions, V. 48, No. 7 (2007), 1901-1906.
 - 16] H.R. Zarei, M. Kröger, "Optimization of the foam-filled aluminum tubes for crush box application", Thin-Walled Structures, 46 (2008) 214-221
 - 17] L. Bonaccorsi, E. Proverbio, N. Raffaele. "Effect of the interface bonding on the mechanical response of aluminium foam reinforced steel tubes", J. Mater. Sci., 45 (2010), 1514-1522
 - 18] N. Michailidis, F. Stergioudi, H. Omar, D.N. Tsipas, "An image-based reconstruction of the 3D geometry of an Al open-cell foam and FEM modeling of the material response", Mechanics of Materials, 42 (2010), 142-147
 - 19] G. Costanza, F. Mantineo, A. Sili, M.E. Tata, "Characterization of Cu tube filled with Al alloy foam by means of X-ray computer tomography", TMS2014 - 143rd Annual Meeting Supplemental Proceedings, San Diego, California (USA), February 16-20, 2014
 - 20] J. Banhart, J. Baumeister, M. Weber, Proc. of the European Conference on Advanced PM Materials, Birmingham, (1995), p.201
 - 21] G. Costanza, G. Gusmano, R. Montanari, M.E. Tata, "Metodi di produzione e applicazioni delle schiume metalliche", La Metallurgia Italiana, n. 2/2003, p. 31-35.
 - 22] G. Costanza, G. Gusmano, R. Montanari, M.E. Tata, N. Ucciardello, "Effect of powder mix composition on Al foam morphology", Proceedings of the Institution of Mechanical Engineers, Part L: Journal of Materials: Design and Applications, 222 (2008), 131-140.
 - 23] G. Costanza, M.E. Tata, "Metal foams: Recent experimental results and further developments", Metallurgia Italiana, Vol. 103 n. 3 (2011), 3-7.
 - 24] G. Costanza, M. E. Tata, Recycling of exhaust batteries in lead-foam electrodes, in REWAS 2013 Enabling Materials Resource Sustainability, Ed. Anne Kvithyld and Christina Meskers, ISBN 978-1-1186-0587-5, pp. 272-278.
 - 25] C. Park, S. R. Nutt, "Effect of process parameters on steel foam synthesis", Materials Science and Engineering, A297 (2001), 62-68
 - 26] P. Jonsén, H.-A. Häggblad, "Fracture energy based constitutive models for tensile fracture of metal powder compacts", International Journal of Solids and Structures, 44 (2007), 6398-6411
 - 27] Proveti, J. and Michot, G., 2006, The Brazilian test: a tool for measuring the toughness of a material and its brittle to ductile transition. Int. J. Fracture, 139 455-460.
 - 28] Ye Jianhong, F.Q. Wu, J.Z. Sun, "Estimation of the tensile elastic modulus using Brazilian disc by applying diametrically opposed concentrated loads", International Journal of Rock Mechanics & Mining Sciences 46 (2009) 568-576
 - 29] J. Banhart, F. Baumgärtner, S. Cox, B. Kronberg, D. Langevin, S. Odenbach, D. Weaire, T. Wübben, "Development of advanced foams under microgravity", 1st International Symposium on Microgravity Research and Applications in Physical Sciences and Biotechnology, 10-15 September 2000, Sorrento, Italy - Proceedings, ESTEC/ESA Publishing Division, Noordwijk, ESA Special Publications SP-454, (2000), 589-596.